

**Research Article**

Copyright © All rights are reserved by Catia Rosana Lange de Aguiar

Botanical Printing of Natural and Synthetic Fabrics: The Role of Mordants in Eco-Printing with Plant-Based Materials

Anika Egelkamp¹, Fernanda Steffens^{2,3}, Jean Carlos Fantoni², Bruna Segatti³, Grazyella Cristina Oliveira de Aguiar², Odinei Hess Gonçalves^{2,3} and Catia Rosana Lange de Aguiar^{2,3*}

¹Faculty of Textile & Clothing Technology, Niederrhein University of Applied Science, Mönchengladbach, Germany

²Department of Textile Engineering, Federal University of Santa Catarina, Blumenau, Brazil

³Graduate Program in Textile Engineering, Federal University of Santa Catarina, Blumenau, Brazil

***Corresponding author:** Catia Rosana Lange de Aguiar, Department of Textile Engineering, Federal University of Santa Catarina, Rua João Pessoa, 2750, Blumenau, Santa Catarina, Brazil.

Received Date: September 18, 2025

Published Date: September 26, 2025

Abstract

The textile industry is one of the largest polluters in the world, with textile dyeing and finishing being particularly harmful to the environment. Major concerns include the use of toxic chemicals and the large volumes of water required to add colour to fabrics. This has led to increasing demand for sustainable and eco-friendly methods of dyeing and printing textiles using natural dyes and processes. This study aims to explore the use of natural dyes extracted from red rose petals, eucalyptus leaves, and yellow onion skins to print on cotton, polyamide, and silk fabrics. Two different techniques were applied to achieve successful botanical prints, employing conventional mordants: copper sulphate and iron oxide. The printed samples were evaluated for colour fastness to washing and dry rubbing. Both botanical printing techniques proved to be suitable for eco-friendly applications. Fabrics printed with onion skin dye demonstrated the best results in terms of washing fastness and aesthetic quality. Polyamide samples exhibited the highest colour intensity with all the natural dyes used. While the mordants had no significant effect on fastness properties, they enhanced colour yield on cotton and silk fabrics.

Keywords: Sustainability; Natural dyes; Botanical printing

Introduction

Natural dyes are sourced from plant extracts, minerals, or animal sources which make them biodegradable, renewable, and environmentally friendly [1]. Natural dyes have a millennium-long history in textiles, which reflects the complex inter-relationships between people, plants, and the environment [2].

Based on their chemical composition, natural dyes are mainly divided into several groups such as tannins, carotenoids, quinoids, alkaloids, anthraquinones, flavonoids and indigonoids [3]. Fruits and vegetables contain molecules with specific colours, which can be an environmentally attractive replacement for their synthetic counterparts in (non)food applications [4]. Onion skins can be

used to create beautiful shades of yellow and brown and can be a way of using kitchen waste for natural dyeing [1]. The dyestuff, which is present in the onion skin, is called pelargonidin (3,5,7,4-tetrahydroxy anthocyanin). Four hydroxyl groups in a molecule act as the auxochrome groups, for the pelargonidin to communicate great dyeing proper-ties.

The natural compound of the anthocyanin is a water-soluble natural pigment, which can be extracted from the red rose. There are more than 300 kinds of anthocyanins giving colours like pink, purple or magenta to the rose petal [5]. Anthocyanins belong to the family of flavonoids, these consist of three cycles, two benzene rings and an oxygenated heterocycle, carrying hydroxyl groups in various positions [6].

The colours obtained with eucalyptus dyeing varied between yellow and brown, depending on the dye concentration, dyeing process, and mordant chosen [7]. The leaves contain up to 11 % of the major components of tannin (gallic acid [3,4,5-trihydroxy benzoic acid], with ellagic acid [2,3,7,8-tetrahydroxy (1) benzopyran (5,4,3-cde) (1) benzopyran-5,10-dione]) and flavonoids (quercetin [3,3',4',5,7-pentahydroxylflavone] and rutin [3,3',4',5,7-pentahydroxylflavone-3-rhamnoglucoside]) as the minor components. Tannins and flavonoids are useful substances during the dyeing process because of their ability to fix dyes within fabrics [8].

Natural dyes have the potential to significantly impact on the future of sustainable textile production and promote a more socially and environmentally responsible sector with sustained improvements and industry-wide initiatives. Literature suggests that there is a major vacuum in research concerning the latest developments and potential applications of natural dyes in textiles materials is the lack of comprehensive studies that tackle the environmental sustainability and scalability of manufacturing and application procedures over the long run [2].

Natural dyes often produce unique, softer, and earthy aesthetics but usually lack the intense brightness obtained with synthetic dyes. Additionally, natural dyes fade faster when exposed to sunlight or washing compared to synthetic dyes which offer excellent colour consistency and stability [1]. To achieve successful and commercial use of natural dyes, appropriate and standardized dyeing techniques need to be adopted without decreasing the required quality of the dyeing fabrics.

The study of Hüseyn Benli emphasized the effect of pretreatment processes on the obtained colour with natural dyes. Bleached and mercerized cotton fabric were dyed by pigment printing method, with the use of extracts obtained from five different natural sources. These were pomegranate peel, nutshell, orange tree leaves, alkanet roots and dyer's chamomile. Instead of mordanting agents, binder was used for fixing natural dye on the fabric and to make this process more environmentally friendly. The results showed that pretreatment processes had great importance in terms of colour efficiency and colour shades. Applying mercerization after bleaching prior to printing process caused a significant increase

in colour efficiencies and darker shades, but the increase in colour saturation could be varied according to the natural dye source used. Natural dyes are usually applied to textiles by dyeing. For producing printed fabrics, a mordant must be applied because natural dyes are mostly non-substantive. Usually a metallic salt is used, having an affinity for both the fibre and the colouring matter [9].

Chemical mordants, such as potassium alum, sodium chloride, ferrous sulphate, calcium chloride, and tannic acid, contribute to the enhancement or darkening of the hue by forming metallic dye complexes in the fabric [10]. The study by Marquardt, et al. showed that dyeing processes with annatto extract are enhanced by mordants such as alum and ferrous (II) sulphate and by polyelectrolyte agents such as PDDACl, which presented excellent colour yields [11].

Another study researched the replacement of conventional mordants by using a natural mordant. Bio-waste chitosan was applied on wool fabric with natural dyes in fine powder form. The results were positive, showing deep and fast prints with chitosan. This natural mordant gave a higher colour value than alum mordant. All-natural dyes exhibited good to excellent washing and light fastness, while the colour fastness properties improved with an increase in mordant concentration. This indicated that chitosan plays an important role as a mordant and was even superior to alum regarding efficacy as a mordant [12].

In this study, two different ways of botanical printing are presented and are compared with the studies carried out so far on the application of natural dyes on textiles substrates. The aim was to investigate the suitability of using yellow onion skin, red rose petals and eucalyptus leaves as natural dyes in printing woven cotton and silk fabrics and knitted polyamide fabric. The selection of mordants was due to the fact that they are cationic elements, which can positively influence the electrostatic attraction of natural dyes to cellulose fibers. The aim of this work is to reduce the application of synthetic dyes and to help people using natural materials and apply these sustainable methods to the textile and dyeing industries. This study is a motivation to optimize current methods and development new techniques of natural dyeing and printing.

Materials and Methods

Materials

In the present work natural pigments from yellow onion skin (*Allium cepa*), red rose petals (*Rosa gallica* L.) and eucalyptus leaves (*Eucalyptus grandis*) were applied to fabrics composed of 100 % silk (woven fabric), 100 % polyamide (knitted fabric) and 98 % cotton and 2 % elastane (woven fabric). Copper sulphate (CuSO_4) and iron oxide (Fe_2O_3) were applied as mordants. Distilled water and non-ionic detergent were also used.

Botanical printing with iron oxide mordant in solution

Before printing, the fabrics and the mordant solution had to be prepared. Therefore, all samples were washed with water and detergent.

For the botanical printing process, the dried fabric sample was placed on a clean surface and the pigments (yellow onion skin, rose petals and eucalyptus leaves) were distributed over 50 % of the fabric's surface (Figure 1a). The fabric was then folded in half so

that the dyes could dye the entire surface of the fabric. In the next step, the fabric was tightly rolled onto an aluminum cylinder, as shown in Figure 1b. After being rolled into the cylinder, the samples were tied with a cotton thread, as shown in Figure 1c.

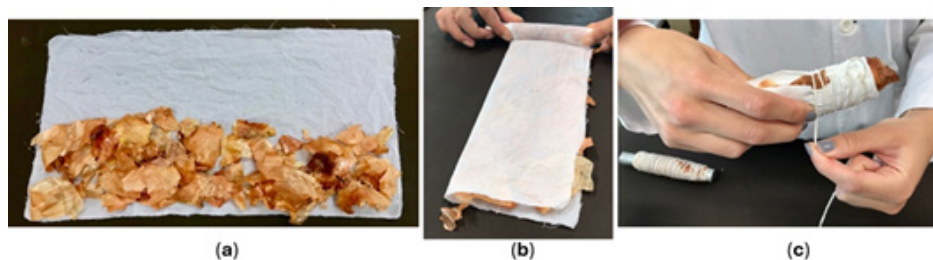


Figure 1: (a) Arrangement of pigments on 50 % of a fabric; (b) rolling the fabric over the cylinder; (c) cylinder with tied fabric.

To continue the printing process, a 2.5% iron oxide mordant solution was prepared, and the pH was adjusted to approximately 6.0. Fabric samples were boiled for 60 minutes using water, with

and without mordant in the solution, to evaluate and compare the effects of the printing on colour fastness. After this step, the fabrics were rinsed in clean water and dried at room temperature.

Botanical printing with copper sulphate mordant on natural elements



Figure 2: Application of mordant on natural elements.

Initially, the fabrics were washed with water and detergent to promote better hydrophilicity. The mordant solution was prepared using a 2.5 % copper sulphate solution. Each natural element (yellow onion peel, eucalyptus leaves, and red rose petals) was immersed in the mordant solution for four hours, as shown in Figure 2.

After the natural elements remained in the mordant solution, they were removed from the solution and immediately add-ed to the fabric samples as described in section 4.2, as well as rolled and tied into cylinders. The samples were boiled for 60 minutes using water and pH was adjusted to approximately 6.0. After that, the fabrics were rinsed in clean water and dried at room temperature, to evaluate and compare the effects of the printing on colour fastness.

Determination of colour fastness to washing

The ISO 105-C06 B2S method was used to determine the colour fastness to washing. The colour transfer is then compared with the

grey scale for dyeing.

The grey scale for colour change was used to indicate the amount of transfer and colour change after washing. The samples printed with copper sulphate mordant were grouped into the following three categories: i) one wash cycle; ii) five wash cycles; iii) ten wash cycles.

Determination of colour crocking fastness

For determination of colour fastness to dry rubbing, ISO method 105-X12:1993 (dry and wet) was followed. Samples were rubbed with a standard white fabric for ten complete cycles and evaluated using the grey scale for dyeing.

Results

Botanical printing with iron oxide mordant in solution

In this method, the prints made with eucalyptus leaves and rose petals on the three fabric samples, with and without mordant,

did not show satisfactory printing results. All samples lost colour, except for the polyamide fabric with the onion skins.

The yellow onion skin applied to polyamide knitted fabric, with and without mordant, showed very satisfactory results. The colours were bright and intense on the fabrics. There was no visual difference between the samples treated with and without mordant,

as seen in Figure 3, which leads us to believe that, in this case, the iron oxide mordant was not necessary to improve the interaction between the onion skin and the fabric. This characteristic can be attributed to the ionic nature of the polyamide, which is cationic, which may have formed an ionic bond with the hydroxyls present in the quercetin in the onion skins.

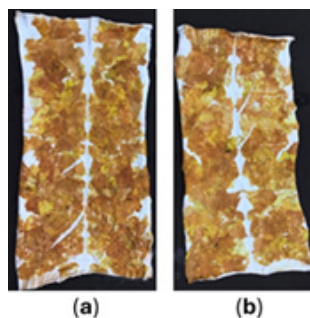


Figure 3: Botanical printing of polyamide fabric with yellow onion skin: (a) with mordant; (b) without mordant.

Mohammad Raza Miah studied the dyeing of wool fabric using natural dye extracts from onion's outer skin by using water and organic solvents. Alum mordant, copper mordant and chrome mordant were chosen for mordanting. The results showed that onion peel could be successfully used for dyeing wool with metallic mordants. The prints obtained a wide range of soft, pastel and light colours. Overall, it can be stated that wool fabric dyeing with extracted onion's outer skin has a good prospect in the textile dyeing industry. This statement can be according to the results obtained in this research applied to polyamide and silk as well [13]. The study of Ashish Debnath confirmed and expanded onion skin's suitability as a natural dye in the textile dyeing sector. Red onion skin was applied on cotton fabric by the exhaust method then dried and cured for a proper fixation. The result was that red onion skin

can dye cotton effectively [4]. The dyes extracted from this type of waste material can be an attractive alternative for synthetic dyes.

Botanical printing with copper sulphate mordant on natural elements

When printing was carried out without copper sulphate mordant, the cotton and silk prints were very light in tone and the plant structure was blurred on the textile substrate. However, when printed with pretreated natural dyes, the prints were deeper and sharper. The plant structure and contours were clearly visible and appeared in vibrant colours, especially on the cotton fabric, as can be seen in Figure 4a. This indicated the positive role of the copper sulphate mordant in imparting affinity to the rose petal pigment on the cotton fabric.

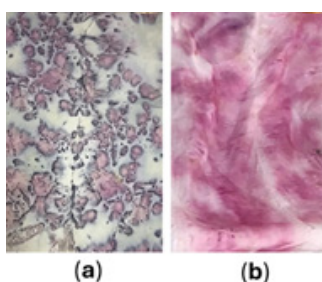


Figure 4: Cotton fabric printed with red rose petals: (a) with mordant; (b) without mordant.

Fabric samples printed with mordant eucalyptus leaves produced satisfactory results on silk fabric. The eucalyptus leaves

left an intensified impression, with colours that highlighted the contour line structure of the plants, as shown in Figure 5.



Figure 5: Mordanted eucalyptus leaves on silk woven fabric.

The study of Rattanaphol Mongkholrattanasit was concerned with dye extraction from the leaves of eucalyptus and the application of this natural dye for silk and wool fabric dyeing by the exhaustion method. This study confirms that silk and wool fabrics can be successfully dyed with eucalyptus leaf extract because of the tannin richness of the eucalyptus leaves. Tannin contains phenolic compounds who can form hydrogen bonds with the carboxyl group of protein fibres. Whereby, wool dyed with eucalyptus leaf extract undertook higher colour strength than silk, which is because wool contains more functional groups (NH₂) than silk fabric. The silk and wool fabrics dyed with the eucalyptus leaf extract, combined with a mordant compound, exhibited a yellowish-brown shade. Exceptions were the fabrics dyed with iron sulphate as mordant, resulting in a shade of dark greyish brown. This research proves that the usage of mordants does not only improve colour strength but also provides shade differences [13].

Among the three fabrics used, polyamide produced the most intense printing result. The copper sulphate mordant improved the

colour intensity and sharpness of the samples, as they appeared radiant with detailed printed structures. However, prints without mordant application also produced coloured prints, however, the colours were lighter in tone compared to those with copper sulphate mordant. This result demonstrates how mordants not only impart affinity to the pigment for polyamide, but in many cases also produce different colours. Figure 6 presents the colour differences between the polyamide samples using different natural pigments with and without the copper sulphate mordant.

Red rose petals and eucalyptus leaves without mordant (Figures 6b and 6d, respectively) presented a less refined result, compared to the samples with mordant (Figures 6a and 6c), due to faded colours, with blurred printed structures. However, the sample printed with rose petals with mordant presented colour intensity and sharpness. Exceptionally, the yellow onion skin (Figures 6e and 6f) presented intense coloration, obtaining colours ranging from bright orange to greenish yellow, in the samples with and without mordant, respectively.

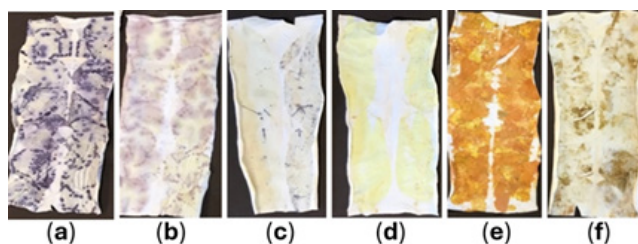


Figure 6: Printed polyamide fabrics: (a) red rose petals with and (b) without mordant; (c) eucalyptus leaves with and (d) without mordant; (e) yellow onion skin with and (f) without mordant.

Fastness results of printed samples

Colour fastness to washing: The colour fastness to washing rating of the printed samples using the method presented in section 2.2 was evaluated and presented as shown in Table 1.

The results of colour fastness to wash according to the gray scale for change and transfer were excellent, both scores 4/5. This indicated that the use of iron oxide mordant did not influence the

fastness properties in printing with yellow onion skin as a natural pigment.

Ashish Debnath's study on cotton-based samples dyed with pelargonidin extruded from red onion skin gave very satisfactory results of colour fastness to washing. Cotton and polyamide obtained the same score of 4/5 [14]. The colour fastness to washing rating of the samples printed using the method presented in section 2.3 was evaluated and presented as shown in Table 2. It is important

to note that only the samples with satisfactory staining results were evaluated.

According to Table 2, the colour fastness to washing considering transfer was excellent, indicating that the use of copper sulphate

mordant had no effect on this property. However, most of the natural pigments changed their colour, i.e., faded or paled after one wash. The exception was the natural dye onion skin on polyamide, as the fastness to washing was excellent, therefore, the natural pigment did not lose its colour.

Table 1: Evaluation of colour fastness to washing using natural onion skin pigment with and without iron oxide mordant.

Sample	Mordant Fe ₂ O ₃	Grayscale fastness	
		change	transfer
Polyamide	with	4/5	4/5
	without	4/5	4/5

Table 2: Evaluation of washing fastness using natural pigments with copper sulphate mordant.

Sample	Natural dye	Mordant CuSO ₄	Grayscale fastness	
			change	transfer
Cotton	rose petals	with	2/3	4/5
Cotton	eucalyptus leaves	with	3	4/5
Polyamide	onion skin	with	4/5	4/5
Polyamide	onion skin	without	5	4/5
Polyamide	rose petals	with	3	4/5
Polyamide	rose petals	without	3	4/5
Polyamide	eucalyptus leaves	with	4	4/5
Silk	eucalyptus leaves	with	2/3	4/5

Colour fastness to washing after 1, 5 and 10 wash cycles:

The samples were subjected to additional wash fastness tests to evaluate and compare the intensity of colour change after the first,

fifth and tenth washes. The colour fastness to washing rating of the samples printed with natural pigments, with and without mordant applied to the pigment is presented in Table 3.

Table 3: Evaluation of washing fastness after 1, 5 and 10 wash cycles.

Sample	Natural dye	Mordant CuSO ₄	Grayscale fastness (change)		
			1 cycle	5 cycles	10 cycles
Cotton	rose petals	with	2/3	2	2
Cotton	eucalyptus leaves	with	3	2	1
Polyamide	onion skin	with	4/5	4	3
Polyamide	onion skin	without	5	5	5
Polyamide	rose petals	with	3	2	2
Polyamide	rose petals	without	3	3	3
Polyamide	eucalyptus leaves	with	4	4	4
Silk	eucalyptus leaves	with	2/3	2/3	2

The highest score was obtained using yellow onion skin on knitted polyamide fabric without copper sulphate mordant. The lowest score was obtained using eucalyptus leaves and mordant on woven cotton fabric. The more wash tests were carried out, the less intense the colour of the print became, resulting in a faded and pale appearance.

Colour fastness to dry rubbing: The classification of colour

fastness to dry rubbing samples printed with natural onion skin pigment, with and without iron oxide mordant on polyamide fabric is presented in Table 4.

The results observed in Table 4 indicate that although the pigment transferred to the control fabric, this transfer was light and satisfactory for a natural pigment (Table 5).

Table 4: Evaluation of colour fastness to dry rubbing using natural onion skin pigment with and without iron oxide mordant.

Sample	Mordant Fe ₂ O ₃	Grayscale fastness
Polyamide	with	4
	without	4

Table 5: presents the results of colour fastness to dry rubbing for fabrics printed with natural pigments without copper sulphate mordant.

Sample	Natural dye	Mordant CuSO ₄	Grayscale fastness
Cotton	rose petals	with	5
Cotton	eucalyptus leaves	with	5
Polyamide	onion skin	with	4/5
Polyamide	onion skin	without	4
Polyamide	rose petals	with	4/5
Polyamide	rose petals	without	4/5
Polyamide	eucalyptus leaves	with	4/5
Silk	eucalyptus leaves	with	5

Conclusions

Botanical printing with mordant applied to the pigment was carried out using copper sulphate as mordant. Yellow onion skin, red rose petals and eucalyptus leaves were applied, achieving an expanded range of colour impressions. The mordant process provided deeper and sharper impressions. Polyamide knitted fabric reacted well with all-natural pigments, obtaining prints with the greatest colour intensity with and without the mordant. Among the three natural pigments, the most promising was yellow onion skin. The outer skin of the plant, combined with polyamide knitted fabric, achieved the highest and brightest colour intensity. In conclusion, natural dyes represent a promising and sustainable alternative to reduce the environmental impact of synthetic dyes in the textile industry. Among them, yellow onion skin stands out as an affordable and environmentally friendly waste product with significant application potential. Although natural dyes do not yet offer the speed or scalability of their synthetic counterparts, they have considerable value in niche sectors such as fashion and handcrafted textiles. Looking ahead, the industry is expected to continue to refine current methods of applying natural dyes and invest in innovative technologies that promote more environmentally responsible dyeing and printing processes.

Acknowledgment

Thanks to Niederrhein University of Applied Science in Germany and to Federal University of Santa Catarina, Brazil.

Conflicts of Interest

The authors declare no conflicts of interest.

References

- Algee EO, Uthman TO (2024) A review of history, properties, classification, applications and challenges of natural and synthetic dyes. *Heliyon* 10(13): e33646.
- Pranta AD, Rahaman Md T (2024) Extraction of eco-friendly natural dyes and biomordants for textile coloration: A critical review. *Nano-Structures & Nano-Objects* 39: 101243.
- Haji A, Naebe M (2020) Cleaner dyeing of textiles using plasma treatment and natural dyes: A review. *Journal of Cleaner Production* 265: 121866.
- Phan K, Raes K, Speybroeck VV, Roosen M, De Clerck K, et al. (2021) Non-food applications of natural dyes extracted from agro-food residues: A critical review. *Journal of Cleaner Production* 301: 126920.
- Gokilamani N, Muthukumarasamy N, Thambidurai M, Ranjitha A, Velauthapillai D, et al. (2013) Dye-sensitized solar cells with natural dyes extracted from rose petals. *J Mater Sci: Mater Electron* 24: 3394-3402.
- Eugster CH, Märki-Fischer E (1991) The Chemistry of Rose Pigments. *Angewandte Chemie International Edition in English* 30(6): 613-622.
- Santiago D, Cunha J, Cabral I (2023) Chromatic and medicinal properties of six natural textile dyes: A review of eucalyptus, weld, madder, annatto, indigo and woad. *Heliyon* 9(11): e22013.
- Mongkhlorattanasit R, Kryštůfek J, Wiener J, Studničková J (2011) Natural dyes from eucalyptus leaves and application for wool fabric dyeing by using padding techniques. In *Natural dyes*, IntechOpen pp. 57-78.
- Bahtiyari MI, Benli H, Yavas A (2017) Use of different natural dye sources for printing of cotton fabrics. *Textile and Apparel* 27(3): 259-265.
- Naqvi SAR, ul-Wara K, Adeel S, Mia R, Hosseinnazhad M, et al. (2024) Modern ecofriendly approach for extraction of luteolin natural dye from weld for silk fabric and wool yarn dyeing. *Sustainable Chemistry and Pharmacy* 39: 101554.
- Marquardt AL, de Oliveira CRS, Volkmann AC, Francisco IBM, da Silva Júnior AH, et al. (2025) Exploring the dyeing potential of annatto dye on linen substrate: An inquiry into the effects of different mordants. *Coloration Technology* 141(3): 405-422.
- Teli MD, Sheikh J, Shastrakar P (2014) Eco-friendly antibacterial printing of wool using natural dyes. *Journal of Textile Science & Engineering* 4(2): 1-5.
- Miah MR, Telegin F, Rahman Md S (2016) Eco-friendly dyeing of wool fabric using natural dye extracted from onion's outer shell by using water and organic solvents. *International Research Journal of Engineering and Technology* 3(9): 450-467.
- Debnath A, Zerín I, Hasan Md M, Sarker N, Ahmed K, et al. (2018) Natural dyeing of cotton fabric by extruded pelargonidin of red onion skin and finished it naturally with *aloe vera*. *Int J Environ Sci Nat Res* 14(2): 555885.